

Concerns : Raw Material

Control Sheet N° :

FCM_2026-0014

Starting date :

02/02/2026

End date :

16/02/2026

Product Characteristics


Supplier:	1295
Raw Material:	Alligator semi-mat ric noir
Finishing:	SAFARI ALLIGATOR
Material reference:	A-RM-02383
Material lot :	A-CM- 0043539

Summary of results

<input checked="" type="checkbox"/> Adhesive Tape	Exfoliation	OK
<input checked="" type="checkbox"/> Folding	Change	OK
<input checked="" type="checkbox"/> Rubbing test on moist state (Veslic)	50 & 100 cycles	5/5
	Colour change & aspect	5/5
<input checked="" type="checkbox"/> Rubbing test on dry state (Veslic)	50 & 100 cycles	4,5/5
	Colour change & aspect	4,5/5
<input checked="" type="checkbox"/> Colour fastness to perspiration	Moist & dry staining	5/5
<input checked="" type="checkbox"/> Colour fastness to artificial light	Colour change	5/5
<input type="checkbox"/> Rubbing test on dry state (artificial sweat, Veslic)	50 & 100 cycles	
	Colour change & aspect	

Comments

Adhesive tape, 3M810

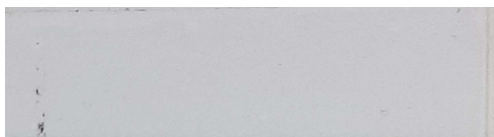


Observations

Exfoliation

OK

No visible alteration

Folding twice

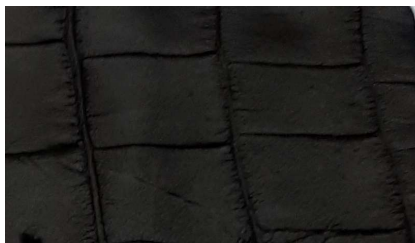

Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

BRASPORT

SWITZERLAND – SINCE 1946

TEST REPORT

Control Sheet N° :

FCM_2026-0014

Rubbing test on moist state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining	Final colour change	Aspect
50 Cycles	5/5	4,5/5
100 Cycles	5/5	

50 Cycles

5/5

4,5/5


5/5

100 Cycles

5/5

No staining of the colour on the felts. No change of the colour at 150 cycles, with slight distortion, slight swelling.

Rubbing test on dry state (Veslic), partial extension

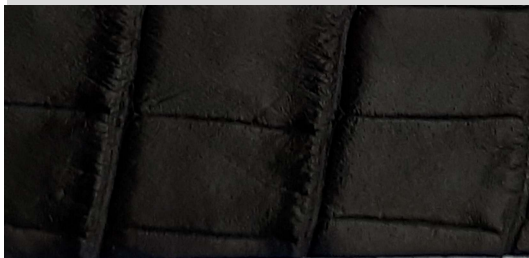

50 cycles



100 cycles



Observations

Felt staining	Final colour change	Aspect
50 Cycles	4,5/5	4,5/5
100 Cycles	5/5	

50 Cycles

4,5/5

4,5/5


4,5/5

100 Cycles

5/5

Very slight staining of the colour on the first felt, no staining on the second. Very slight change of the colour at 150 cycles, with slight shiny aspect depending on the orientation.

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2

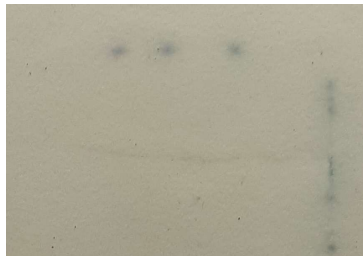

Observations

Staining on blotting paper

Moist state	Dry state
5/5	5/5

On dry state, no staining staining of the colour on the blotting paper from the surface, intense and point staining on the blotting paper from cutting edges. Very slight change of the colour on the tested sample, cotation 4,5, with increase of the relief.

Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension



50 cycles



100 cycles



Felt staining	Final colour change	Aspect
50 Cycles		
100 Cycles		

50 Cycles

100 Cycles


Observations

Colour change

5/5

No change of the colour on the exposed area.

Colour fastness to artificial light, approx. 7,8 MJ/m², metal halide lamp

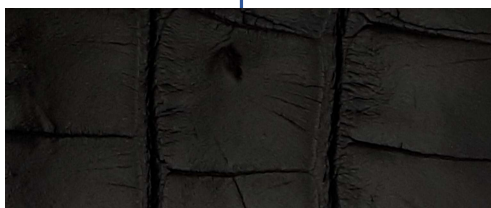

TEST REPORT

Control Sheet N° :

FCM_2026-0014

Starting date : 02/02/2026

Chromium VI test	Observations
	Upper limit < 3 ppm
pH test	
	Value

Standards references

Adhesive Tape	Designation
INS-23-239-D-e / SWATCH GROUP ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration Slight and sparse exfoliation visible on tape, nothing visible on material.
	KO Slight finishing removal, visible on tape and material. Evident exfoliation and removal of numerous finishing particules on tape and material. Finishing and underlying material removal.

Folding	Designation
Inhouse Method ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration.
	OK Aesthetic and visual alteration with formation of slight wrinkles.
	To assess by the customer Aesthetic and visual alteration of color with formation of slight wrinkles.
	KO Formation of wrinkles and cracks of the finishing.
	KO Formation of wrinkles and finishing peeling off. Exfoliation of finishing with tearing of underlying material.

Rubbing tests (moist, dry, artificial sweat, veslic)

Colour fastness to perspiration

INS-23-229-C-e / SWATCH GROUP
 ISO 2419, Preparation and sample conditioning
ISO 11640, Colour fastness to cycles of to-and-fro rubbing
ISO 105-A02, Greyscale for assessing change in colour
ISO 105-A03, Greyscale for assessing staining

INS-23-221-E-e / SWATCH GROUP
PRO052 / AQC
 NIHS 96-50, Chemical and climatic resistance of a watch case
 ISO 2419, Preparation and sample conditioning
ISO 105-A02, Greyscale for assessing change in colour
ISO 105-A03, Greyscale for assessing staining

Colour fastness to artificial light	Cosmetic Products Resistance
-------------------------------------	------------------------------

INS-23-230-D-e / SWATCH GROUP
 ISO 2419, Preparation and sample conditioning
 NIHS 96-50, Chemical and climatic resistance of a watch case
ISO 105-A02, Greyscale for assessing change in colour

Inhouse Method (drop test)
NIHS 96-50, Chemical and climatic resistance of a watch case
Common used products :
 Waterproof NIVEA SUN SPRAY, factor 20
 Hugo Boss perfume, HUGO
 Anti Brumm Forte insect repellent, containing N,N-diethyl-m-toluamide (No CAS : 134-62-3)

Carried out by : Isabelle Brun

Modified by :

Date: