

Concerns : Raw Material

Control Sheet N° :

FCM_2026-0217

Starting date :

05/05/2026

End date :

24/06/2026

Product Characteristics


Supplier:	1295
Raw Material:	alligator semi-mat ric rouge bordeaux
Finishing:	SAFARI ALLIGATOR
Material reference:	A-RM-02901
Material lot :	A-CM- 0044101

Summary of results

☒ Adhesive Tape	Exfoliation	OK
☒ Folding	Change	OK
☒ Rubbing test on moist state (Veslic)	50 & 100 cycles	4,5/5
	Colour change & aspect	5/5
☒ Rubbing test on dry state (Veslic)	50 & 100 cycles	5/5
	Colour change & aspect	4,5/5
☒ Colour fastness to perspiration	Moist & dry staining (plain material or scales)	5/5
	Moist & dry staining (interscale spaces)	5/5
☒ Colour fastness to artificial light	Colour change	3,5/5
☐ Rubbing test on dry state (artificial sweat, Veslic)	50 & 100 cycles	
	Colour change & aspect	

Comments

Adhesive tape, 3M810

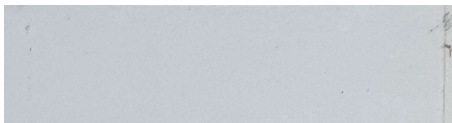

Observations

Exfoliation

OK

No visible alteration

Folding twice



Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

BRASPORT

SWITZERLAND — SINCE 1946

TEST REPORT

Control Sheet N° :

FCM_2026-0217

Rubbing test on moist state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

3,5/5

4,5/5

100 Cycles

4/5

Very slight staining of the colour on the first felt, slight and heterogeneous on the second. No change of the colour at 150 cycles, with stains on interscale spaces, cotation 4.

Rubbing test on dry state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

4,5/5

4,5/5

5/5

100 Cycles

5/5

No staining of the colour on the felts. Very slight change of the colour at 150 cycles, with very slight shiny appearance depending on the orientation.

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2



Observations

Staining on blotting paper

Moist state

Dry state

5/5

(plain material or scales)

5/5

5/5

(interscale spaces)

5/5

On dry state, no staining staining of the colour on the blotting paper from the scales, no staining staining of the colour on the blotting paper from the interscale spaces, moderate staining on the blotting paper from cutting edges. Moderate change of the colour on the tested sample, cotation 3, with darker appearance, increase of the relief.

Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension

50 cycles

100 cycles

Felt staining

Final colour change

Aspect

50 Cycles

100 Cycles


Observations

Colour change

3,5/5

Slight to moderate change of the colour on the exposed area.

Colour fastness to artificial light, approx. 7,8 MJ/m², metal halide lamp

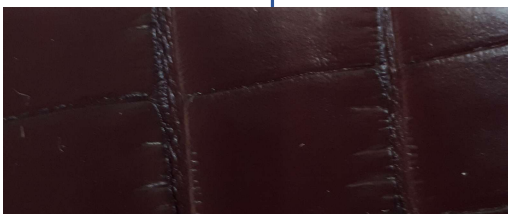

TEST REPORT

Control Sheet N° :

FCM_2026-0217

Starting date : 05/05/2026

Chromium VI test	Observations
	Upper limit < 3 ppm
pH test	
	Value

Standards references		
Adhesive Tape		Designation
REF034 : customer protocol REF008 : ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK	No visible alteration
		Slight and sparse exfoliation visible on tape, nothing visible on material.
	KO	Slight finishing removal, visible on tape and material.
		Evident exfoliation and removal of numerous finishing particules on tape and material.
		Finishing and underlying material removal.
Folding		Designation
INS015 : Inhouse Method REF008 : ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK	No visible alteration.
	OK	Aesthetic and visual alteration with formation of slight wrinkles.
	To assess by the customer	Aesthetic and visual alteration of color with formation of slight wrinkles.
	KO	Formation of wrinkles and cracks of the finishing.
	KO	Formation of wrinkles and finishing peeling off.
	KO	Exfoliation of finishing with tearing of underlying material.
Rubbing tests (moist, dry, artificial sweat, veslic)		Colour fastness to perspiration

REF032 : customer protocol
 REF008 : ISO 2419, Preparation and sample conditioning
REF032 : ISO 11640, Colour fastness to cycles of to-and-fro rubbing
REF004 : ISO 105-A02, Greyscale for assessing change in colour
REF005 : ISO 105-A03, Greyscale for assessing staining

REF029 : customer protocol
REF041 : AQC protocol
 REF026 : NIHS 96-50, Chemical and climatic resistance of a watch case
 REF008 : ISO 2419, Preparation and sample conditioning
REF004 : ISO 105-A02, Greyscale for assessing change in colour
REF005 : ISO 105-A03, Greyscale for assessing staining

Colour fastness to artificial light	Cosmetic Products Resistance
REF033 : customer protocol REF008 : ISO 2419, Preparation and sample conditioning REF026 : NIHS 96-50, Chemical and climatic resistance of a watch case REF004 : ISO 105-A02 , Greyscale for assessing change in colour	Inhouse Method (drop test) REF029 : NIHS 96-50 , Chemical and climatic resistance of a watch case Common used products : Waterproof NIVEA SUN SPRAY, factor 20 Hugo Boss perfume, HUGO Anti Brumm Forte insect repellent, containing N,N-diethyl-m-toluamide (No CAS : 134-62-3)

Carried out by : Isabelle Brun

Modified by :

Date: