

Concerns : Raw Material

Control Sheet N° :

FCM_2025-0017

Starting date : 06/01/2025 End date :

Product Characteristics

Supplier:	1098
Raw Material:	Alligator nacré bleu 0653
Finishing:	Nacré / Perlé ALLIGATOR
Material reference:	A-RM-03330
Material lot :	A-CM- 0041244

Summary of results

<input checked="" type="checkbox"/>	Adhesive Tape		OK
<input checked="" type="checkbox"/>	Folding		OK
<input checked="" type="checkbox"/>	Rubbing test on moist state (Veslic)	50 & 100 cycles	5/5 5/5
<input checked="" type="checkbox"/>	Colour change	Aspect	5/5 5/5
<input checked="" type="checkbox"/>	Rubbing test on dry state (Veslic)	50 & 100 cycles	5/5 5/5
<input checked="" type="checkbox"/>	Colour change	Aspect	5/5 5/5
<input checked="" type="checkbox"/>	Colour fastness to perspiration		5/5
<input checked="" type="checkbox"/>	Colour fastness to artificial light		3,5/5
<input type="checkbox"/>	Rubbing test on moist state (artificial sweat, Veslic)	50 & 100 cycles	
<input type="checkbox"/>	Colour change	Aspect	

Comments

Adhesive tape, 3M810



Observations

Exfoliation

OK

No visible alteration

Folding twice



Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

BRASPORT


SWITZERLAND – SINCE 1946

TEST REPORT

Control Sheet N° :

FCM_2025-0017

Rubbing test on moist state (Veslic), partial extension

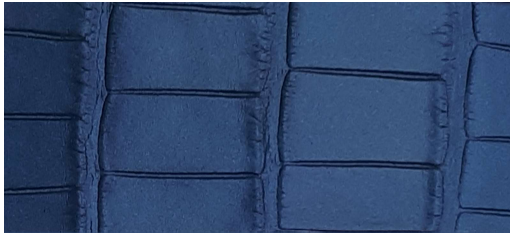

50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

5/5

5/5

No staining of the colour on the felts. No change of the colour at 150 cycles.

100 Cycles

5/5

Rubbing test on dry state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

5/5


5/5

No staining of the colour on the felts. No change of the colour at 150 cycles.

100 Cycles

5/5

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2

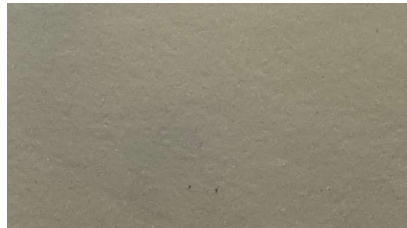

Observations

Staining on blotting paper

5/5

No staining of the colour on the blotting paper from the surface. Slight staining of the colour on the blotting paper from cutting edges, cotation 4/5. Slight change of the colour on tested sample, cotation 4.

Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension

50 cycles

100 cycles

Felt staining

Final colour change

Aspect

50 Cycles

100 Cycles

Colour fastness to artificial light, approx. 7,8 MJ/m², metal halide lamp



Observations

Colour change

3,5/5

Slight to moderate change of the colour on the exposed area.

