

# BRASPORT

SWITZERLAND – SINCE 1946

## TEST REPORT

Concerns : Raw Material

Control Sheet N° :

FCM\_2025-0141

Starting date :

12/03/2025

End date :

07/04/2025

### Product Characteristics


Supplier:	1295
Raw Material:	Alligator semi-mat ric gold green
Finishing:	<b>Safari</b> <b>ALLIGATOR</b>
Material reference:	A-RM-03522
Material lot :	A-CM- 0041671

### Summary of results

<input checked="" type="checkbox"/> Adhesive Tape			OK
<input checked="" type="checkbox"/> Folding			OK
<input checked="" type="checkbox"/> Rubbing test on moist state (Veslic)	50 & 100 cycles	5/5	5/5
<input checked="" type="checkbox"/> Colour change	Aspect	5/5	5/5
<input checked="" type="checkbox"/> Rubbing test on dry state (Veslic)	50 & 100 cycles	5/5	5/5
<input checked="" type="checkbox"/> Colour change	Aspect	5/5	5/5
<input checked="" type="checkbox"/> Colour fastness to perspiration			4,5/5
<input checked="" type="checkbox"/> Colour fastness to artificial light			3,5/5
<input type="checkbox"/> Rubbing test on moist state (artificial sweat, Veslic)	50 & 100 cycles		
<input type="checkbox"/> Colour change	Aspect		

### Comments

#### Adhesive tape, 3M810

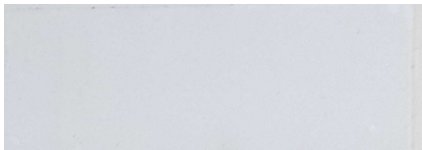

#### Observations

Exfoliation

OK

No visible alteration

#### Folding twice



#### Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

# BRASPORT

SWITZERLAND – SINCE 1946

## TEST REPORT

Control Sheet N° :

FCM\_2025-0141

### Rubbing test on moist state (Veslic), partial extension



50 cycles



100 cycles



### Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

5/5


5/5

No staining of the colour on the felts. No change of the colour at 150 cycles.

100 Cycles

5/5

### Rubbing test on dry state (Veslic), partial extension

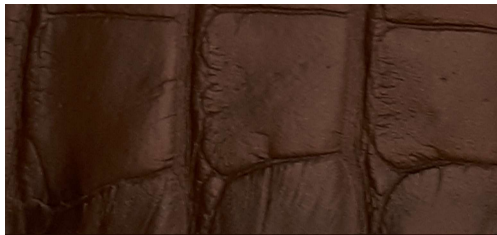

50 cycles



100 cycles



### Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

5/5


5/5

No staining of the colour on the felts. No change of the colour at 150 cycles.

100 Cycles

5/5

### Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2

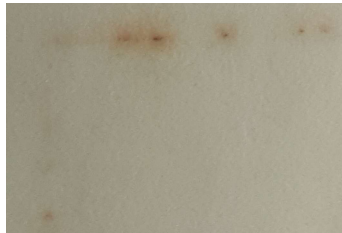

### Observations

Staining on blotting paper

4,5/5

Very slight staining of the colour on the blotting paper from the surface (interscale spaces). Significant to intense and point staining of the colour on the blotting paper from cutting edges, cotation 1,5/5. Slight to moderate change of the colour on the tested sample, cotation 2,5

### Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension

50 cycles

100 cycles

Felt staining

Final colour change

Aspect

50 Cycles

100 Cycles

### Observations

Colour change

3,5/5

Slight to moderate change of the colour on the exposed area.

### Colour fastness to artificial light, approx. 7,8 MJ/m<sup>2</sup>, metal halide lamp



