

Concerns : Raw Material

Control Sheet N° :

FCM_2026-0024

Starting date :

16/01/2026

End date :

23/01/2026

Product Characteristics

Supplier:	1265
Raw Material:	Alligator nubuck gris terre
Finishing:	NUBUCK ALLIGATOR
Material reference:	A-RM-03670
Material lot :	B-CM- 0029571

Summary of results

<input checked="" type="checkbox"/> Adhesive Tape	Exfoliation	OK	
<input checked="" type="checkbox"/> Folding	Change	OK	
<input checked="" type="checkbox"/> Rubbing test on moist state (Veslic)	50 & 100 cycles	5/5	4,5/5
	Colour change & aspect	4/5	3,5/5
<input checked="" type="checkbox"/> Rubbing test on dry state (Veslic)	50 & 100 cycles	4/5	4/5
	Colour change & aspect	4/5	3,5/5
<input checked="" type="checkbox"/> Colour fastness to perspiration	Moist & dry staining	2/5	2,5/5
<input checked="" type="checkbox"/> Colour fastness to artificial light	Colour change	3,5/5	
<input type="checkbox"/> Rubbing test on dry state (artificial sweat, Veslic)	50 & 100 cycles		
	Colour change & aspect		

Comments

Observed stainings and changes are inherent to the finishing of the tested material.

Adhesive tape, 3M810

Observations



Exfoliation

OK

Exfoliation visible on tape, nothing visible on material.

Folding twice

Observations



Change

OK


No visible alteration.

TEST REPORT

Control Sheet N° :	FCM_2026-0024
--------------------	---------------

Rubbing test on moist state (Veslic), 500 grams


Observations

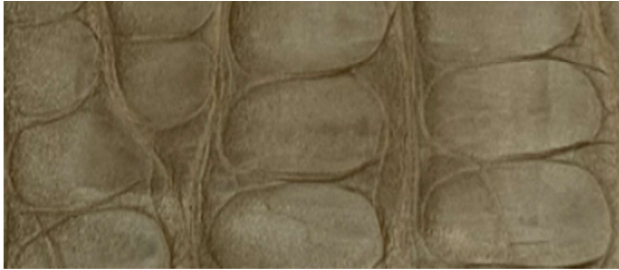

Felt staining	Final colour change	Aspect
50 Cycles	4/5	3,5/5
5/5	No staining of the colour on the first felt, very slight on the second. Slight change of the colour at 150 cycles, with wear.	
100 Cycles		
4,5/5		

Rubbing test on dry state (Veslic), 500 grams

Observations



Felt staining	Final colour change	Aspect
50 Cycles	4/5	3,5/5
4/5	Slight staining of the colour on the felts. Slight change of the colour at 150 cycles, with wear.	
100 Cycles		
4/5		

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2

Observations



Staining on blotting paper	
Moist state	Dry state
2/5	2,5/5

On dry state, moderate to significant staining of the colour on the blotting paper from the surface, no staining on the blotting paper from cutting edges. Slight change of the colour on the tested sample, cotation 4, with darkening.

Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), 500 grams

Observations



Felt staining	Final colour change	Aspect
50 Cycles		
100 Cycles		

Colour fastness to artificial light, approx. 7,8 MJ/m², xenon lamp

Observations



Colour change
3,5/5

Slight to moderate change of the colour on the exposed area.

TEST REPORT

Control Sheet N° : FCM_2026-0024

Starting date : 16/01/2026

Chromium VI test

Observations

Upper limit
< 3 ppm

pH test

Value

Standards references

Adhesive Tape

Designation

INS-23-239-D-e / SWATCH GROUP

ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning

OK

No visible alteration

Slight and sparce exfoliation visible on tape, nothing visible on material.

KO

Slight finishing removal, visible on tape and material.

Evident exfoliation and removal of numerous finishing particules on tape and material.

Finishing and underlying material removal.

Folding

Designation

Inhouse Method

ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning

OK

No visible alteration.

OK

Aesthetic and visual alteration with formation of slight wrinkles.

To assess by the customer

Aesthetic and visual alteration of color with formation of slight wrinkles.

KO

Formation of wrinkles and cracks of the finishing.

KO

Formation of wrinkles and finishing peeling off.

KO

Exfoliation of finishing with tearing of underlying material.

Rubbing tests (moist, dry, artificial sweat, veslic)

Colour fastness to perspiration

INS-23-229-C-e / SWATCH GROUP

ISO 2419, Preparation and sample conditioning

ISO 11640, Colour fastness to cycles of to-and-fro rubbing

ISO 105-A02, Greyscale for assessing change in colour

ISO 105-A03, Greyscale for assessing staining

INS-23-221-E-e / SWATCH GROUP

PRO052 / AQC

NIHS 96-50, Chemical and climatic resistance of a watch case

ISO 2419, Preparation and sample conditioning

ISO 105-A02, Greyscale for assessing change in colour

ISO 105-A03, Greyscale for assessing staining

Colour fastness to artificial light

Cosmetic Products Resistance

INS-23-230-D-e / SWATCH GROUP

ISO 2419,Preparation and sample conditioning

NIHS 96-50, Chemical and climatic resistance of a watch case

ISO 105-A02, Greyscale for assessing change in colour

Inhouse Method (drop test)

NIHS 96-50, Chemical and climatic resistance of a watch case

Common used products :

Waterproof NIVEA SUN SPRAY, factor 20

Hugo Boss perfume, HUGO

Anti Brumm Forte insect repellent, containing N,N-diethyl-m-toluamide (No CAS : 134-62-3)

Carried out by : Beatriz Silva

Modified by :

Date: