

Concerns : Raw Material

Control Sheet N° :

FCM_2026-0080

Starting date :

16/03/2026

End date :

31/03/2026

Product Characteristics


Supplier:	1098
Raw Material:	Alligator mat soft I marine moyen
Finishing:	SAFARI ALLIGATOR
Material reference:	A-RM-03851
Material lot :	A-CM- 0043641

Summary of results

<input checked="" type="checkbox"/> Adhesive Tape	Exfoliation	OK	
<input checked="" type="checkbox"/> Folding	Change	OK	
<input checked="" type="checkbox"/> Rubbing test on moist state (Veslic)	50 & 100 cycles	4,5/5	4,5/5
	Colour change & aspect	4,5/5	4/5
<input checked="" type="checkbox"/> Rubbing test on dry state (Veslic)	50 & 100 cycles	5/5	5/5
	Colour change & aspect	5/5	4/5
<input checked="" type="checkbox"/> Colour fastness to perspiration	Moist & dry staining <small>(plain material or scales)</small>	5/5	5/5
	Moist & dry staining <small>(interscale spaces)</small>	3/5	3,5/5
<input checked="" type="checkbox"/> Colour fastness to artificial light	Colour change	4/5	
<input type="checkbox"/> Rubbing test on dry state (artificial sweat, Veslic)	50 & 100 cycles		
	Colour change & aspect		

Comments

Adhesive tape, 3M810



Observations

Exfoliation

OK

No visible alteration

Folding twice



Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

BRASPORT

SWITZERLAND – SINCE 1946

TEST REPORT

Control Sheet N° :

FCM_2026-0080

Rubbing test on moist state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

4,5/5

4/5

4,5/5

100 Cycles

4,5/5

Very slight staining of the colour on the felts. Very slight change of the colour at 150 cycles, with very slight wear on top of scales, slightly stained with water.

Rubbing test on dry state (Veslic), partial extension



50 cycles



100 cycles



Observations

Felt staining

Final colour change

Aspect

50 Cycles

5/5

4/5


5/5

100 Cycles

5/5

No staining of the colour on the felts. No change of the colour at 150 cycles, with straightening of the scales.

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2

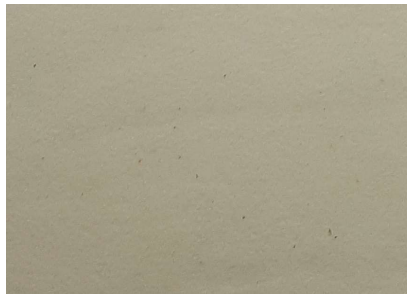

Observations

Staining on blotting paper

Moist state

Dry state

5/5

(plain material or scales)

5/5

3/5

(interscale spaces)

3,5/5

On dry state, no staining of the colour on the blotting paper from the scales, slight to moderate staining of the colour on the blotting paper from the interscale spaces, no staining on the blotting paper from cutting edges. Slight to moderate change of the colour on the tested sample, cotation 3,5, with darker appearance, slight increase of the relief.

Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension

50 cycles

100 cycles

Felt staining


Final colour change

Aspect

50 Cycles

100 Cycles

Colour fastness to artificial light, approx. 7,8 MJ/m², metal halide lamp

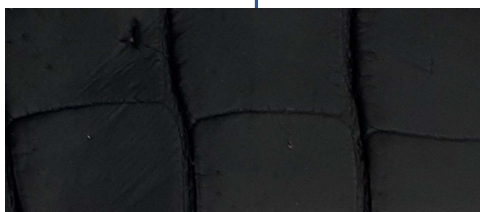

Observations

Colour change

4/5

Slight change of the colour on the exposed area.

TEST REPORT

Control Sheet N° :

FCM_2026-0080

Starting date : 16/03/2026

Chromium VI test	Observations
	Upper limit < 3 ppm
pH test	
	Value

Standards references

Adhesive Tape	Designation
REF034 : customer protocol REF008 : ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration Slight and sparse exfoliation visible on tape, nothing visible on material.
	KO Slight finishing removal, visible on tape and material. Evident exfoliation and removal of numerous finishing particules on tape and material. Finishing and underlying material removal.

Folding	Designation
INS015 : Inhouse Method REF008 : ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration.
	OK Aesthetic and visual alteration with formation of slight wrinkles.
	To assess by the customer Aesthetic and visual alteration of color with formation of slight wrinkles.
	KO Formation of wrinkles and cracks of the finishing.
	KO Formation of wrinkles and finishing peeling off. Exfoliation of finishing with tearing of underlying material.

Rubbing tests (moist, dry, artificial sweat, veslic)

Colour fastness to perspiration

REF032 : customer protocol
 REF008 : ISO 2419, Preparation and sample conditioning
REF032 : ISO 11640, Colour fastness to cycles of to-and-fro rubbing
REF004 : ISO 105-A02, Greyscale for assessing change in colour
REF005 : ISO 105-A03, Greyscale for assessing staining

REF029 : customer protocol
REF041 : AQC protocol
 REF026 : NIHS 96-50, Chemical and climatic resistance of a watch case
 REF008 : ISO 2419, Preparation and sample conditioning
REF004 : ISO 105-A02, Greyscale for assessing change in colour
REF005 : ISO 105-A03, Greyscale for assessing staining

Colour fastness to artificial light	Cosmetic Products Resistance
-------------------------------------	------------------------------

REF033 : customer protocol
 REF008 : ISO 2419, Preparation and sample conditioning
 REF026 : NIHS 96-50, Chemical and climatic resistance of a watch case
REF004 : ISO 105-A02, Greyscale for assessing change in colour

Inhouse Method (drop test)
REF029 : NIHS 96-50, Chemical and climatic resistance of a watch case
Common used products :
 Waterproof NIVEA SUN SPRAY, factor 20
 Hugo Boss perfume, HUGO
 Anti Brumm Forte insect repellent, containing N,N-diethyl-m-toluamide (No CAS : 134-62-3)

Carried out by : Isabelle Brun

Modified by :

Date: