

Concerns : Raw Material

Control Sheet N° :

FCM_2026-0058

Starting date :

24/02/2026

End date :

31/03/2026

Product Characteristics

Supplier:	1265
Raw Material:	Alligator high shiny lie de vin
Finishing:	High shiny ALLIGATOR
Material reference:	A-RM-03852
Material lot :	A-CM- 0043618

Summary of results

<input checked="" type="checkbox"/> Adhesive Tape	Exfoliation	OK
<input checked="" type="checkbox"/> Folding	Change	OK
<input checked="" type="checkbox"/> Rubbing test on moist state (Veslic)	50 & 100 cycles	2,5/5 1,5/5
	Colour change & aspect	1,5/5 1,5/5
<input checked="" type="checkbox"/> Rubbing test on dry state (Veslic)	50 & 100 cycles	5/5 4,5/5
	Colour change & aspect	5/5 5/5
<input checked="" type="checkbox"/> Colour fastness to perspiration	Moist & dry staining	5/5 5/5
<input checked="" type="checkbox"/> Colour fastness to artificial light	Colour change	2,5/5
<input type="checkbox"/> Rubbing test on dry state (artificial sweat, Veslic)	50 & 100 cycles	
	Colour change & aspect	

Comments

Adhesive tape, 3M810



Observations

Exfoliation

OK

No visible alteration

Folding twice



Observations

Change

OK

Aesthetic and visual alteration with formation of slight wrinkles.

BRASPORT


SWITZERLAND – SINCE 1946

TEST REPORT

Control Sheet N° :

FCM_2026-0058

Rubbing test on moist state (Veslic), partial extension

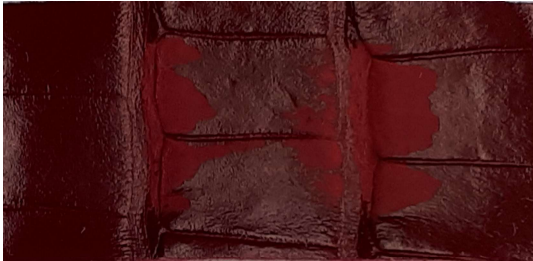

50 cycles



100 cycles



Observations		
Felt staining	Final colour change	Aspect
50 Cycles (*)	1,5/5	1,5/5
2,5/5	Moderate to significant staining of the colour on the first felt, significant to intense on the second. Significant to intense change of the colour at 150 cycles, with decrease of the softness, partial wear of the finishing, slight swelling.	
100 Cycles (*)		

(*) : presence of particules

Rubbing test on dry state (Veslic), partial extension



50 cycles



100 cycles



Observations		
Felt staining	Final colour change	Aspect
50 Cycles	5/5	5/5
5/5	No staining of the colour on the first felt, very slight on the second. No change of the colour at 150 cycles.	
100 Cycles		

Colour fastness to perspiration, 72 hours, ambient temperature, artificial sweat according to ISO 3160-2



Observations		
Staining on blotting paper		
Moist state	Dry state	
5/5	5/5	
On dry state, no staining staining of the colour on the blotting paper from the surface, intense staining on the blotting paper from cutting edges. Slight to moderate change of the colour on the tested sample, cotation 3,5, with decrease of the brightness, increase of the relief, clearer appearance.		


Rubbing test on moist state (Artificial sweat ISO 3160-2, Veslic), partial extension

50 cycles

100 cycles

Observations		
Felt staining	Final colour change	Aspect
50 Cycles		
100 Cycles		

Colour fastness to artificial light, approx. 7,8 MJ/m², metal halide lamp

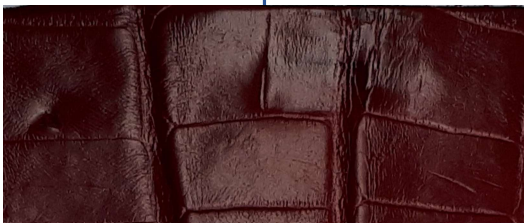

Observations		
Colour change		
2,5/5		

TEST REPORT

Control Sheet N° :

FCM_2026-0058

Starting date : 24/02/2026

Chromium VI test	Observations
	Upper limit < 3 ppm
pH test	Value

Standards references

Adhesive Tape	Designation
INS-23-239-D-e / SWATCH GROUP ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration Slight and sparse exfoliation visible on tape, nothing visible on material.
	KO Slight finishing removal, visible on tape and material. Evident exfoliation and removal of numerous finishing particules on tape and material. Finishing and underlying material removal.

Folding	Designation
Inhouse Method ISO 2419, Physical and mechanicals trials -Preparation and sample conditioning	OK No visible alteration.
	OK Aesthetic and visual alteration with formation of slight wrinkles.
	To assess by the customer Aesthetic and visual alteration of color with formation of slight wrinkles.
	KO Formation of wrinkles and cracks of the finishing.
	KO Formation of wrinkles and finishing peeling off. Exfoliation of finishing with tearing of underlying material.

Rubbing tests (moist, dry, artificial sweat, veslic)

Colour fastness to perspiration

INS-23-229-C-e / SWATCH GROUP
 ISO 2419, Preparation and sample conditioning
ISO 11640, Colour fastness to cycles of to-and-fro rubbing
ISO 105-A02, Greyscale for assessing change in colour
ISO 105-A03, Greyscale for assessing staining

INS-23-221-E-e / SWATCH GROUP
PRO052 / AQC
 NIHS 96-50, Chemical and climatic resistance of a watch case
 ISO 2419, Preparation and sample conditioning
ISO 105-A02, Greyscale for assessing change in colour
ISO 105-A03, Greyscale for assessing staining

Colour fastness to artificial light	Cosmetic Products Resistance
INS-23-230-D-e / SWATCH GROUP ISO 2419, Preparation and sample conditioning NIHS 96-50, Chemical and climatic resistance of a watch case ISO 105-A02 , Greyscale for assessing change in colour	Inhouse Method (drop test) NIHS 96-50 , Chemical and climatic resistance of a watch case Common used products : Waterproof NIVEA SUN SPRAY, factor 20 Hugo Boss perfume, HUGO Anti Brumm Forte insect repellent, containing N,N-diethyl-m-toluamide (No CAS : 134-62-3)

Carried out by : Isabelle Brun

Modified by :

Date: